

# **MATERIALS FOR CIVIL AND CONSTRUCTION ENGINEERS**

**4<sup>th</sup> Edition**

**Michael S. Mamlouk  
Arizona State University**

**John P. Zaniewski  
West Virginia University**

**Solutions Manual**

## FOREWORD

This solutions manual includes the solutions to numerical problems at the end of various chapters of the book. It does not include answers to word questions, but the appropriate sections in the book are referenced. The procedures used in the solutions are taken from the corresponding chapters and sections of the text. Each step in the solution is taken to the lowest detail level consistent with the level of the text, with a clear progression between steps. Each problem solution is self-contained, with a minimum of dependence on other solutions. The final answer of each problem is printed in bold.

Instructors are advised not to spread the solutions electronically among students in order not to limit the instructor's choice to assign problems in future semesters.

*This work is protected by United States copyright laws  
and is provided solely for the use of instructors in teaching  
their courses and assessing student learning. Dissemination  
or sale of any part of this work (including on the World Wide Web)  
will destroy the integrity of the work and is not permitted.*

## CHAPTER 1. MATERIALS ENGINEERING CONCEPTS

1.2. Strength at rupture = **45 ksi**

$$\text{Toughness} = (45 \times 0.003) / 2 = \mathbf{0.0675 \text{ ksi}}$$

1.3.  $A = 0.6 \times 0.6 = 0.36 \text{ in}^2$

$$\sigma = 50,000 / 0.36 = 138,888.9 \text{ psi}$$

$$\varepsilon_a = 0.007 / 2 = 0.0035 \text{ in/in}$$

$$\varepsilon_l = -0.001 / 0.6 = -0.0016667 \text{ in/in}$$

$$E = 138,888.9 / 0.0035 = \mathbf{39,682,543 \text{ psi} = 39,683 \text{ ksi}}$$

$$\nu = 0.00166667 / 0.0035 = \mathbf{0.48}$$

1.4.  $A = 201.06 \text{ mm}^2$

$$\sigma = 0.945 \text{ GPa}$$

$$\varepsilon_A = 0.002698 \text{ m/m}$$

$$\varepsilon_L = -0.000625 \text{ m/m}$$

$$E = 350.3 \text{ GPa}$$

$$\nu = \mathbf{0.23}$$

1.5.  $A = \pi d^2 / 4 = 28.27 \text{ in}^2$

$$\sigma = P / A = -150,000 / 28.27 \text{ in}^2 = -5.31 \text{ ksi}$$

$$E = \sigma / \varepsilon = 8000 \text{ ksi}$$

$$\varepsilon_A = \sigma / E = -5.31 \text{ ksi} / 8000 \text{ ksi} = -0.0006631 \text{ in/in}$$

$$\Delta L = \varepsilon_A L_o = -0.0006631 \text{ in/in} (12 \text{ in}) = -0.00796 \text{ in}$$

$$L_f = \Delta L + L_o = 12 \text{ in} - 0.00796 \text{ in} = \mathbf{11.992 \text{ in}}$$

$$\nu = -\varepsilon_L / \varepsilon_A = 0.35$$

$$\varepsilon_L = \Delta d / d_o = -\nu \varepsilon_A = -0.35 (-0.0006631 \text{ in/in}) = 0.000232 \text{ in/in}$$

$$\Delta d = \varepsilon_L d_o = 0.000232 (6 \text{ in}) = 0.00139 \text{ in}$$

$$d_f = \Delta d + d_o = 6 \text{ in} + 0.00139 \text{ in} = \mathbf{6.00139 \text{ in}}$$

1.6.  $A = \pi d^2 / 4 = 0.196 \text{ in}^2$

$$\sigma = P / A = 2,000 / 0.196 \text{ in}^2 = 10.18 \text{ ksi} \text{ (Less than the yield strength. Within the elastic region)}$$

$$E = \sigma / \varepsilon = 10,000 \text{ ksi}$$

$$\varepsilon_A = \sigma / E = 10.18 \text{ ksi} / 10,000 \text{ ksi} = 0.0010186 \text{ in/in}$$

$$\Delta L = \varepsilon_A L_o = 0.0010186 \text{ in/in} (12 \text{ in}) = 0.0122 \text{ in}$$

$$L_f = \Delta L + L_o = 12 \text{ in} + 0.0122 \text{ in} = \mathbf{12.0122 \text{ in}}$$

$$\nu = -\varepsilon_L / \varepsilon_A = 0.33$$

$$\varepsilon_L = \Delta d / d_o = -\nu \varepsilon_A = -0.33 (0.0010186 \text{ in/in}) = -0.000336 \text{ in/in}$$

$$\Delta d = \varepsilon_L d_o = -0.000336 (0.5 \text{ in}) = -0.000168 \text{ in}$$

$$d_f = \Delta d + d_o = 0.5 \text{ in} - 0.000168 \text{ in} = \mathbf{0.49998 \text{ in}}$$

1.7.  $L_x = 30 \text{ mm}$ ,  $L_y = 60 \text{ mm}$ ,  $L_z = 90 \text{ mm}$

$$\sigma_x = \sigma_y = \sigma_z = \sigma = 100 \text{ MPa}$$

$$E = 70 \text{ GPa}$$

$$\nu = 0.333$$

$$\epsilon_x = [\sigma_x - \nu (\sigma_y + \sigma_z)] / E$$

$$\epsilon_x = [100 \times 10^6 - 0.333 (100 \times 10^6 + 100 \times 10^6)] / 70 \times 10^9 = 4.77 \times 10^{-4} = \epsilon_y = \epsilon_z = \epsilon$$

$$\Delta L_x = \epsilon \times L_x = 4.77 \times 10^{-4} \times 30 = 0.01431 \text{ mm}$$

$$\Delta L_y = \epsilon \times L_y = 4.77 \times 10^{-4} \times 60 = 0.02862 \text{ mm}$$

$$\Delta L_z = \epsilon \times L_z = 4.77 \times 10^{-4} \times 90 = \mathbf{0.04293 \text{ mm}}$$

$$\begin{aligned} \Delta V &= \text{New volume} - \text{Original volume} = [(L_x - \Delta L_x) (L_y - \Delta L_y) (L_z - \Delta L_z)] - L_x L_y L_z \\ &= (30 - 0.01431) (60 - 0.02862) (90 - 0.04293) - (30 \times 60 \times 90) = 161768 - 162000 \\ &= \mathbf{-232 \text{ mm}^3} \end{aligned}$$

1.8.  $L_x = 4 \text{ in}$ ,  $L_y = 4 \text{ in}$ ,  $L_z = 4 \text{ in}$

$$\sigma_x = \sigma_y = \sigma_z = \sigma = 15,000 \text{ psi}$$

$$E = 1000 \text{ ksi}$$

$$\nu = 0.49$$

$$\epsilon_x = [\sigma_x - \nu (\sigma_y + \sigma_z)] / E$$

$$\epsilon_x = [15 - 0.49 (15 + 15)] / 1000 = 0.0003 = \epsilon_y = \epsilon_z = \epsilon$$

$$\Delta L_x = \epsilon \times L_x = 0.0003 \times 15 = 0.0045 \text{ in}$$

$$\Delta L_y = \epsilon \times L_y = 0.0003 \times 15 = 0.0045 \text{ in}$$

$$\Delta L_z = \epsilon \times L_z = 0.0003 \times 15 = 0.0045 \text{ in}$$

$$\begin{aligned} \Delta V &= \text{New volume} - \text{Original volume} = [(L_x - \Delta L_x) (L_y - \Delta L_y) (L_z - \Delta L_z)] - L_x L_y L_z \\ &= (15 - 0.0045) (15 - 0.0045) (15 - 0.0045) - (15 \times 15 \times 15) = 3371.963 - 3375 \\ &= \mathbf{-3.037 \text{ in}^3} \end{aligned}$$

1.9.  $\epsilon = 0.3 \times 10^{-16} \sigma^3$

$$\text{At } \sigma = 50,000 \text{ psi, } \epsilon = 0.3 \times 10^{-16} (50,000)^3 = 3.75 \times 10^{-3} \text{ in./in.}$$

$$\text{Secant modulus} = \frac{\Delta \sigma}{\Delta \epsilon} = \frac{50,000}{3.75 \times 10^{-3}} = \mathbf{1.33 \times 10^7 \text{ psi}}$$

$$\frac{d\epsilon}{d\sigma} = 0.9 \times 10^{-16} \sigma^2$$

$$\text{At } \sigma = 50,000 \text{ psi, } \frac{d\epsilon}{d\sigma} = 0.9 \times 10^{-16} (50,000)^2 = 2.25 \times 10^{-7} \text{ in.}^2/\text{lb}$$

$$\text{Tangent modulus} = \frac{d\sigma}{d\epsilon} = \frac{1}{2.25 \times 10^{-7}} = \mathbf{4.44 \times 10^6 \text{ psi}}$$

$$1.11. \epsilon_{\text{lateral}} = \frac{-3.25 \times 10^{-4}}{1} = -3.25 \times 10^{-4} \text{ in./in.}$$

$$\epsilon_{\text{axial}} = \frac{2 \times 10^{-3}}{2} = 1 \times 10^{-3} \text{ in./in.}$$

$$\nu = -\frac{\epsilon_{\text{lateral}}}{\epsilon_{\text{axial}}} = -\frac{-3.25 \times 10^{-4}}{1 \times 10^{-3}} = \mathbf{0.325}$$

$$1.12. \epsilon_{\text{axial}} = 0.05 / 50 = 0.001 \text{ in./in.}$$

$$\epsilon_{\text{lateral}} = -\nu \times \epsilon_{\text{axial}} = -0.33 \times 0.001 = -0.00033 \text{ in./in.}$$

$$\Delta d = \epsilon_{\text{lateral}} \times d_0 = -0.00033 \times 0.025 = -0.00000825 \text{ in. (Contraction)}$$

$$1.13. L = 380 \text{ mm}$$

$$D = 10 \text{ mm}$$

$$P = 24.5 \text{ kN}$$

$$\sigma = P/A = P/\pi r^2$$

$$\sigma = 24,500 \text{ N} / \pi (5 \text{ mm})^2 = 312,000 \text{ N/mm}^2 = 312 \text{ Mpa}$$

The copper and aluminum can be eliminated because they have stresses larger than their yield strengths as shown in the table below.

$$\text{For steel and brass, } \delta = \frac{PL}{AE} = \frac{24,500 \text{ lb} \times 380 \text{ mm}}{\pi (5 \text{ mm})^2 E (\text{kPa})} = \frac{118,539}{E (\text{MPa})} \text{ mm}$$

Material	Elastic Modulus (MPa)	Yield Strength (MPa)	Tensile Strength (MPa)	Stress (MPa)	$\delta$ (mm)
Copper	110,000	248	289	312	
Al. alloy	70,000	255	420	312	
Steel	207,000	448	551	312	0.573
Brass alloy	101,000	345	420	312	1.174

The problem requires the following two conditions:

a. No plastic deformation  $\Rightarrow$  Stress < Yield Strength

b. Increase in length,  $\delta < 0.9 \text{ mm}$

The only material that satisfies both conditions is **steel**.

$$1.14. \sigma = \frac{F}{A_0} = \frac{7,000}{\pi (0.3)^2} = 24,757 \text{ psi} = 24.757 \text{ ksi}$$

This stress is less than the yield strengths of all metals listed.

$$\Delta l = \frac{\sigma L_0}{E}$$

Material	E (ksi)	Yield Strength (ksi)	Tensile Strength (ksi)	$\Delta L$ (in.)
Steel alloy 1	26,000	125	73	0.014
Steel alloy 2	29,000	58	36	0.013
Titanium alloy	16,000	131	106	0.023
Copper	17,000	32	10	0.022

Only the steel alloy 1 and steel alloy 2 have elongation less than 0.018 in.

$$1.15. \quad \sigma = \frac{F}{A_0} = \frac{31,000 \text{ N}}{\pi \left( \frac{15.24 \times 10^{-2} \text{ m}}{2} \right)^2} = 169.9 = 170 \text{ MPa}$$

This stress is less than the yield strengths of all metals listed.

$$\Delta l = \frac{\sigma L_0}{E}$$

Material	E (GPa)	Yield Strength (MPa)	Tensile Strength (MPa)	$\Delta L$ (mm)
Steel alloy 1	180	860	502	0.378
Steel alloy 2	200	400	250	0.340
Titanium alloy	110	900	730	0.618
Copper	117	220	70	0.581

Only the steel alloy 1 and steel alloy 2 have elongation less than 0.45 mm.

- 1.16. a.  $E = \sigma / \epsilon = 40,000 / 0.004 = \mathbf{10 \times 10^6 \text{ psi}}$   
 b. Tangent modulus at a stress of 45,000 psi is the slope of the tangent at that stress =  $\mathbf{4.7 \times 10^6 \text{ psi}}$   
 c. Yield stress using an offset of 0.002 strain =  $\mathbf{49,000 \text{ psi}}$   
 d. Maximum working stress = Failure stress / Factor of safety =  $49,000 / 1.5 = \mathbf{32,670 \text{ psi}}$

- 1.17. a. Modulus of elasticity within the linear portion =  $\mathbf{20,000 \text{ ksi}}$ .  
 b. Yield stress at an offset strain of 0.002 in./in.  $\approx \mathbf{70.0 \text{ ksi}}$   
 c. Yield stress at an extension strain of 0.005 in/in.  $\approx \mathbf{69.5 \text{ ksi}}$   
 d. Secant modulus at a stress of 62 ksi.  $\approx \mathbf{18,000 \text{ ksi}}$   
 e. Tangent modulus at a stress of 65 ksi.  $\approx \mathbf{6,000 \text{ ksi}}$

1.18. a. Modulus of resilience = the area under the elastic portion of the stress strain curve =  $\frac{1}{2}(50 \times 0.0025) \approx \mathbf{0.0625 \text{ ksi}}$

b. Toughness = the area under the stress strain curve (using the trapezoidal integration technique)  $\approx \mathbf{0.69 \text{ ksi}}$

c.  $\sigma = 40 \text{ ksi}$ , this stress is within the elastic range, therefore,  $E = \mathbf{20,000 \text{ ksi}}$

$$\epsilon_{\text{axial}} = 40/20,000 = 0.002 \text{ in./in.}$$

$$\nu = -\frac{\epsilon_{\text{lateral}}}{\epsilon_{\text{axial}}} = -\frac{-0.00057}{0.002} = \mathbf{0.285}$$

d. The permanent strain at 70 ksi =  $\mathbf{0.0018 \text{ in./in.}}$

1.19.

	Material A	Material B
a. Proportional limit	<b>51 ksi</b>	<b>40 ksi</b>
b. Yield stress at an offset strain of 0.002 in./in.	<b>63 ksi</b>	<b>52 ksi</b>
c. Ultimate strength	<b>132 ksi</b>	<b>73 ksi</b>
d. Modulus of resilience	<b>0.065 ksi</b>	<b>0.07 ksi</b>
e. Toughness	<b>8.2 ksi</b>	<b>7.5 ksi</b>
f.	Material B is more ductile as it undergoes more deformation before failure	

1.20. Assume that the stress is within the linear elastic range.

$$\sigma = \epsilon \cdot E = \frac{\delta \cdot E}{l} = \frac{0.3 \times 16,000}{10} = 480 \text{ ksi}$$

Thus  $\sigma > \sigma_{\text{yield}}$

Therefore, the applied stress is not within the linear elastic region, and it is not possible to compute the magnitude of the load that is necessary to produce the change in length based on the given information.

1.21. Assume that the stress is within the linear elastic range.

$$\sigma = \varepsilon \cdot E = \frac{\delta \cdot E}{l} = \frac{7.6 \times 105,000}{250} = 3,192 \text{ MPa}$$

Thus  $\sigma > \sigma_{\text{yield}}$

Therefore, the applied stress is not within the linear elastic region and it is not possible to compute the magnitude of the load that is necessary to produce the change in length based on the given information.

1.22. At  $\sigma = 60,000 \text{ psi}$ ,  $\varepsilon = \sigma / E = 60,000 / (30 \times 10^6) = 0.002 \text{ in./in.}$

a. For a strain of 0.001 in./in.:

$$\varepsilon = \sigma / E = 0.001 \times 30 \times 10^6 = \mathbf{30,000 \text{ psi}}$$
 (for both i and ii)

b. For a strain of 0.004 in./in.:

$$\sigma = \mathbf{60,000 \text{ psi}}$$
 (for i)

$$\sigma = 60,000 + 2 \times 10^6 (0.004 - 0.002) = \mathbf{64,000 \text{ psi}}$$
 (for ii)

1.23. a. Slope of the elastic portion =  $600/0.003 = 2 \times 10^5 \text{ MPa}$

$$\text{Slope of the plastic portion} = (800-600)/(0.07-0.003) = 2,985 \text{ MPa}$$

$$\text{Strain at 650 MPa} = 0.003 + (650-600)/2,985 = 0.0198 \text{ m/m}$$

$$\text{Permanent strain at 650 MPa} = 0.0198 - 650/(2 \times 10^5) = \mathbf{0.0165 \text{ m/m}}$$

b. Percent increase in yield strength =  $100(650-600)/600 = \mathbf{8.3\%}$

c. The strain at 625 MPa =  $625/(2 \times 10^5) = \mathbf{0.003125 \text{ m/m}}$

This strain is elastic.

1.24. a.  $\sigma_{\text{max}} = \frac{F}{A_0} = \frac{39,872 \text{ N}}{100 \times 10^6 \text{ m}^2} = 0.000399 \text{ Pa} = 398 \text{ MPa}$

$$\text{b. } E = \frac{\sigma}{\varepsilon} = \frac{\sigma \times L_0}{\Delta L} = \frac{\sigma \times L_0}{(L - L_0)}$$

$$E \times (L - L_0) = \sigma \times L_0$$

$$110 \times 10^3 \text{ MPa} \times (67.21 \text{ mm} - L_0) = 398 \text{ MPa} \times L_0$$

$$L_0 = \mathbf{66.97 \text{ mm}}$$



$$1.25. a. \sigma_{max} = \frac{F}{A_o} = \frac{8,944}{0.24} = 37,266.667 \text{ psi}$$

$$b. E = \frac{\sigma}{\epsilon} = \frac{\sigma \times L_o}{\Delta L} = \frac{\sigma \times L_o}{(L - L_o)}$$

$$E \times (L - L_o) = \sigma \times L_o$$

$$16 \times 10^6 \times (3.28 - L_o) = 37,266.667 \times L_o$$

$$L_o = 3.27 \text{ in.}$$

$$1.26. \epsilon_a = \frac{-\epsilon_l}{V} = \frac{-\Delta d}{d} = \frac{-\Delta d}{dV}$$

$$E = \frac{\sigma_a}{\epsilon_a} = \frac{\frac{F}{\left(\frac{\pi d^2}{4}\right)}}{\frac{-\Delta d}{dV}} = \frac{-4FdV}{\pi d^2 \Delta d}$$

$$F = \frac{-d\Delta d \pi E}{4V}$$

$$F = \frac{-(19 \times 10^{-3} \text{ m})(-3.0 \times 10^{-6} \text{ m})(\pi) \left(110 \times 10^9 \frac{\text{N}}{\text{m}^2}\right)}{4(0.35)} = 14,070 \text{ N}$$

$$1.27. \epsilon_a = \frac{-\epsilon_l}{V} = \frac{-\Delta d}{d} = \frac{-\Delta d}{dV}$$

$$E = \frac{\sigma_a}{\epsilon_a} = \frac{\frac{F}{\left(\frac{\pi d^2}{4}\right)}}{\frac{-\Delta d}{dV}} = \frac{-4FdV}{\pi d^2 \Delta d}$$

$$F = \frac{-d\Delta d \pi E}{4V}$$

$$F = \frac{-(0.5 \text{ in.})(-1 \times 10^{-4} \text{ in.})(\pi)(16 \times 10^6 \text{ psi})}{4(0.35)} = 1,795 \text{ lb}$$

1.28. See Sections 1.2.3, 1.2.4 and 1.2.5.

**1.29.** The stresses and strains can be calculated as follows:


$$\sigma = P/A_o = 150 / (\pi \times 2^2) = 11.94 \text{ psi}$$

$$\epsilon = (H_o - H)/H_o = (6 - H)/6$$


The stresses and strains are shown in the following table:

Time (min.)	H (in.)	Strain (in./in.)	Stress (psi)
0	6	0.00000	11.9366
0.01	5.9916	0.00140	11.9366
2	5.987	0.00217	11.9366
5	5.9833	0.00278	11.9366
10	5.9796	0.00340	11.9366
20	5.9753	0.00412	11.9366
30	5.9725	0.00458	11.9366
40	5.9708	0.00487	11.9366
50	5.9696	0.00507	11.9366
60	5.9688	0.00520	11.9366
60.01	5.9772	0.00380	0.0000
62	5.9807	0.00322	0.0000
65	5.9841	0.00265	0.0000
70	5.9879	0.00202	0.0000
80	5.9926	0.00123	0.0000
90	5.9942	0.00097	0.0000
100	5.9954	0.00077	0.0000
110	5.9959	0.00068	0.0000
120	5.9964	0.00060	0.0000

a. Stress versus time plot for the asphalt concrete sample

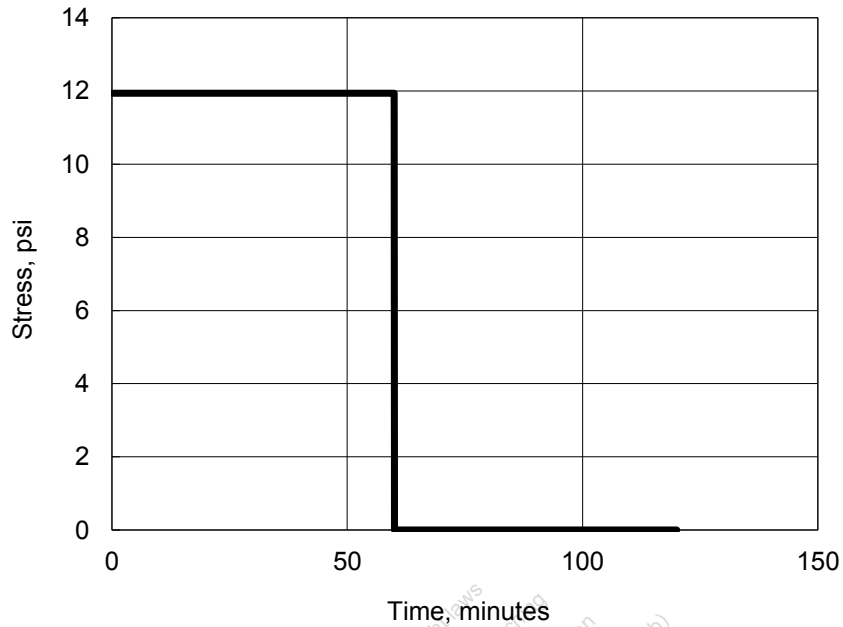

Strain versus time plot for the asphalt concrete sample

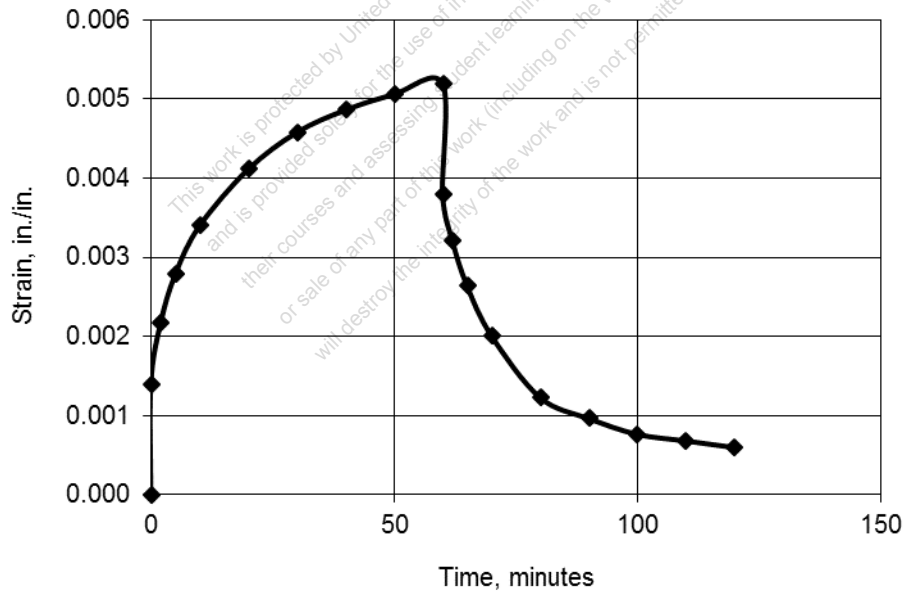

b. Elastic strain = **0.0014 in./in.**

c. The permanent strain at the end of the experiment = **0.0006 in./in.**

d. The phenomenon of the change of specimen height during static loading is called **creep** while the phenomenon of the change of specimen height during unloading called is called **recovery**.

1.30. See Figure 1.12(a).

1.31. a. For  $F \leq F_0$ :  $\delta = F \cdot t / \beta$   
 For  $F > F_0$ , movement

b. For  $F \leq F_0$ :  $\delta = F / M$   
 For  $F > F_0$ :  $\delta = F / M + (F - F_0) t / \beta$

1.32. See Section 1.2.7.

1.34. a. For  $P = 5 \text{ kN}$

$$\text{Stress} = P / A = 5000 / (\pi \times 5^2) = 63.7 \text{ N/mm}^2 = 63.7 \text{ MPa}$$

$$\text{Stress} / \text{Strength} = 63.7 / 290 = 0.22$$

From Figure 1.16, an **unlimited number** of repetitions can be applied without fatigue failure.

b. For  $P = 11 \text{ kN}$

$$\text{Stress} = P / A = 11000 / (\pi \times 5^2) = 140.1 \text{ N/mm}^2 = 140.1 \text{ MPa}$$

$$\text{Stress} / \text{Strength} = 140.1 / 290 = 0.48$$

From Figure 1.16,  $N \approx 700$

1.35. See Section 1.2.8.

1.36.

Material	Specific Gravity
Steel	7.9
Aluminum	2.7
Aggregates	2.6 - 2.7
Concrete	2.4
Asphalt cement	1 - 1.1

1.37. See Section 1.3.2.

$$1.38. \delta L = \alpha_L \times \delta T \times L = 12.5\text{E-}06 \times (115-15) \times 200/1000 = 0.00025 \text{ m} = 250 \text{ microns}$$

$$\text{Rod length} = L + \delta L = 200,000 + 250 = \mathbf{200,250 \text{ microns}}$$

**Compute change in diameter linear method**

$$\delta d = \alpha_d \times \delta T \times d = 12.5\text{E-}06 \times (115-15) \times 20 = 0.025 \text{ mm}$$

$$\text{Final } d = \mathbf{20.025 \text{ mm}}$$

### Compute change in diameter volume method

$$\delta V = \alpha_V \times \delta T \times V = (3 \times 12.5 \times 10^{-6}) \times (115 - 15) \times \pi (10/1000)^2 \times 200/1000 = 2.3562 \times 10^{-11} \text{ m}^3$$

$$\text{Rod final volume} = V + \delta V = \pi r^2 L + \delta V = 6.28319 \times 10^{13} + 2.3562 \times 10^{11} = 6.31 \times 10^{13} \text{ m}^3$$

$$\text{Final } d = \mathbf{20.025 \text{ mm}}$$

There is no stress acting on the rod because the rod is free to move.

- 1.39.** Since the rod is snugly fitted against two immovable nonconducting walls, the length of the rod will not change, **L = 200 mm**

From problem 1.25,  $\delta L = 0.00025 \text{ m}$

$$\epsilon = \delta L / L = 0.00025 / 0.2 = 0.00125 \text{ m/m}$$

$$\sigma = \epsilon E = 0.00125 \times 207,000 = \mathbf{258.75 \text{ MPa}}$$

The stress induced in the bar will be compression.

- 1.40. a.** The change in length can be calculated using Equation 1.9 as follows:

$$\delta L = \alpha_L \times \delta T \times L = 1.1 \times 10^{-5} \times (5 - 40) \times 4 = \mathbf{-0.00154 \text{ m}}$$

- b. The tension load needed to return the length to the original value of 4 meters can be calculated as follows:

$$\epsilon = \delta L / L = -0.00154 / 4 = -0.000385 \text{ m/m}$$

$$\sigma = \epsilon E = -0.000385 \times 200,000 = -77 \text{ MPa}$$

$$P = \sigma \times A = -77 \times (100 \times 50) = -3,850,000 \text{ N} = \mathbf{-385 \text{ kN (tension)}}$$

- c. Longitudinal strain under this load = **0.000385 m/m**

- 1.41.** If the bar was fixed at one end and free at the other end, the bar would have contracted and no stresses would have developed. In that case, the change in length can be calculated using Equation 1.9 as follows.

$$\delta L = \alpha_L \times \delta T \times L = 0.000005 \times (0 - 100) \times 50 = -0.025 \text{ in.}$$

$$\epsilon = \delta L / L = 0.025 / 50 = 0.0005 \text{ in./in.}$$

Since the bar is fixed at both ends, the length of the bar will not change. Therefore, a tensile stress will develop in the bar as follows.

$$\sigma = \epsilon E = -0.0005 \times 5,000,000 = -2,500 \text{ psi}$$

Thus, the tensile strength should be larger than **2,500 psi** in order to prevent cracking.

- 1.43.** See Section 1.7.

1.44. See Section 1.7.1

1.45.  $H_0: \mu \geq 32.4 \text{ MPa}$

$H_1: \mu < 32.4 \text{ MPa}$

$\alpha = 0.05$

$$T_o = \frac{\bar{x} - \mu}{(\sigma / \sqrt{n})} = -3$$

Degree of freedom =  $\nu = n - 1 = 15$

From the statistical t-distribution table,  $T_{\alpha, \nu} = T_{0.05, 15} = -1.753$

$T_o < T_{\alpha, \nu}$

Therefore, **reject** the hypothesis. The contractor's claim is not valid.

1.46.  $H_0: \mu \geq 5,000 \text{ psi}$

$H_1: \mu < 5,000 \text{ psi}$

$\alpha = 0.05$

$$T_o = \frac{\bar{x} - \mu}{(\sigma / \sqrt{n})} = -2.236$$

Degree of freedom =  $\nu = n - 1 = 19$

From the statistical t-distribution table,  $T_{\alpha, \nu} = T_{0.05, 19} = -1.729$


$T_o < T_{\alpha, \nu}$

Therefore, **reject** the hypothesis. The contractor's claim is not valid.

$$1.47. \quad \bar{x} = \frac{\sum_{i=1}^n x_i}{n} = \frac{\sum_{i=1}^{20} x_i}{20} = \frac{113,965}{20} = 5,698.25 \text{ psi}$$
$$s = \left( \frac{\sum_{i=1}^n (x_i - \bar{x})^2}{n-1} \right)^{1/2} = \left( \frac{\sum_{i=1}^{20} (x_i - 5698.25)^2}{20-1} \right)^{1/2} = 571.35 \text{ psi}$$

$$\text{Coefficient of Variation} = 100 \left( \frac{s}{\bar{x}} \right) = 100 \left( \frac{571.35}{5698.25} \right) = 10.03\%$$

b. The control chart is shown below.

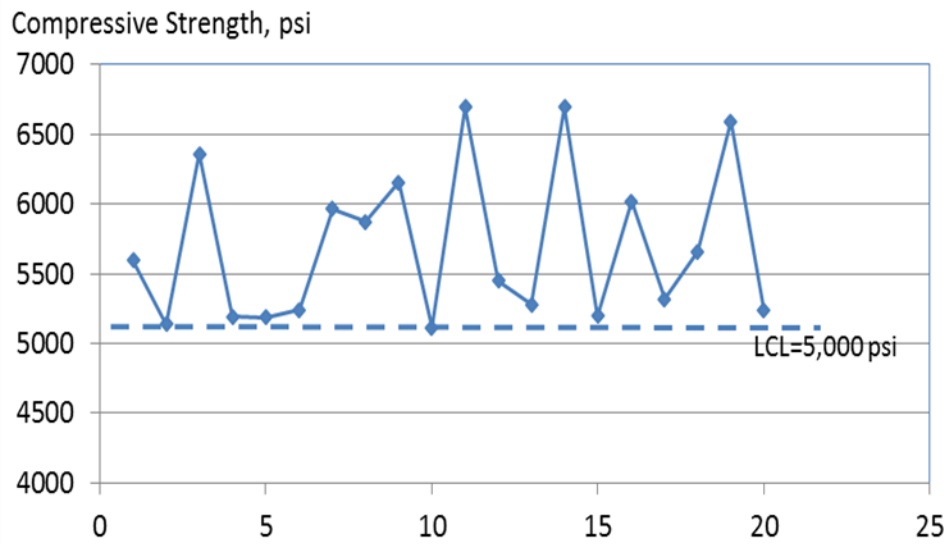

The target value is any value above the specification limit of 5,000 psi. The plant production is meeting the specification requirement.


*This work is protected by United States copyright laws and is provided solely for the use of instructors in teaching their courses and assessing student learning. Dissemination or sale of any part of this work (including on the World Wide Web) will destroy the integrity of the work and is not permitted.*

$$1.48. \text{ a. } \bar{x} = \frac{\sum_{i=1}^n x_i}{n} = \frac{\sum_{i=1}^{20} x_i}{20} = \frac{110.7}{20} = 5.5 \%$$

$$s = \left( \frac{\sum_{i=1}^n (x_i - \bar{x})^2}{n-1} \right)^{1/2} = \left( \frac{\sum_{i=1}^{20} (x_i - 5.5)^2}{20-1} \right)^{1/2} = 0.33 \%$$

$$C = 100 \left( \frac{s}{\bar{x}} \right) = 100 \left( \frac{0.33}{5.5} \right) = 6 \%$$

b. The control chart is shown below.

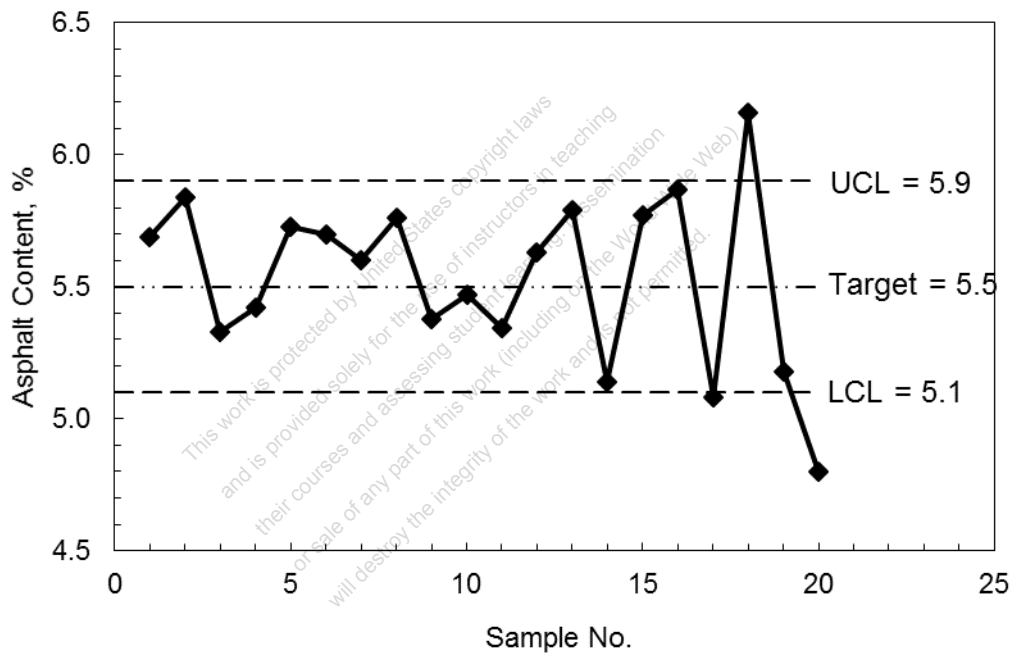

The control chart shows that most of the samples have asphalt content within the specification limits. Only few samples are outside the limits. The plot shows no specific trend, but large variability especially in the last several samples.

1.49. See Section 1.8.2.

1.50. See Section 1.8.




- 1.51.** a. No information is given about accuracy.
- b. Sensitivity == **0.001 in.**
- c. Maximum reading =  $0.001 \times 100 \times 10 = 1$  in.  
Range = **0 – 1 inch**
- d. Accuracy can be improved by calibration.

- 1.52.** a. No information is given about accuracy.
- b. Sensitivity == **0.002 mm**
- c. Maximum reading =  $0.002 \times 20 \times 25 = 1$  mm  
Range = **0 – 1 mm**
- d. Accuracy can be improved by calibration.

- 1.53.** a. 0.001 in.  
b. 100 psi  
c. 100 MPa  
d. 0.1 g  
e. 10 psi  
f. 0.1 %  
g. 0.1 %  
h. 0.001  
i. 100 miles  
j.  $10^{-6}$  mm

This work is protected by United States copyright laws  
and is provided solely for the use of instructors in teaching  
their courses and assessing student learning. Dissemination  
or sale of any part of this work (including on the World Wide Web)  
will destroy the integrity of the work and is not permitted.

1.54. The voltage is plotted versus displacement is shown below.

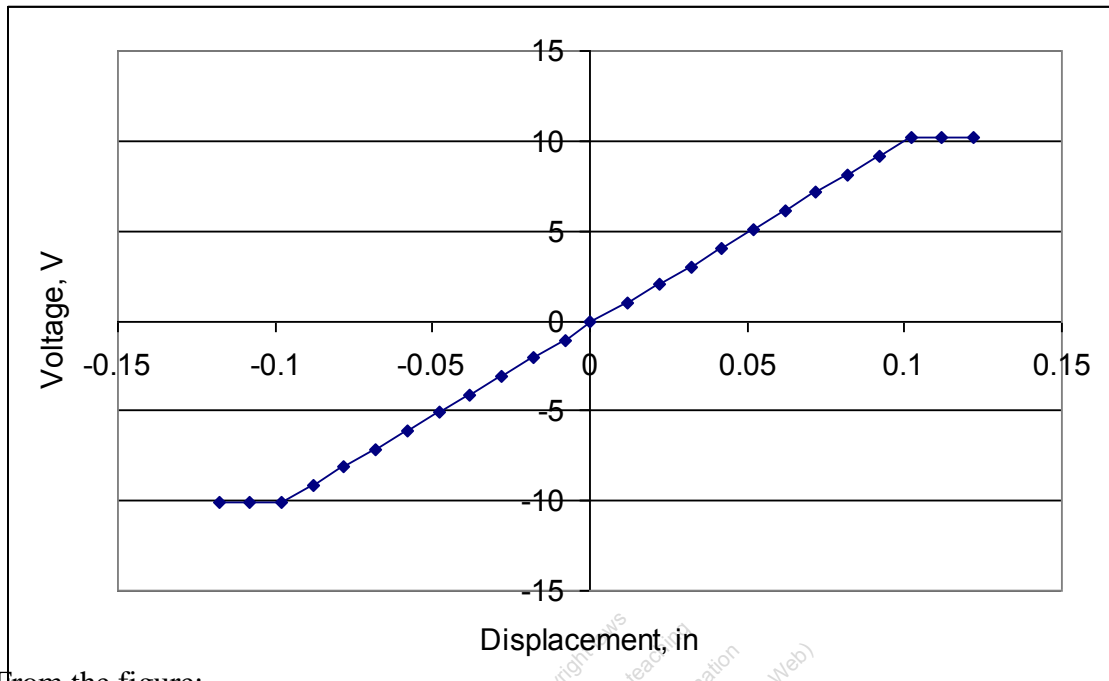


From the figure:

Linear range =  $\pm 0.1$  in.

Calibration factor = 101.2 Volts/in.

1.55. The voltage plotted versus displacement is shown below.

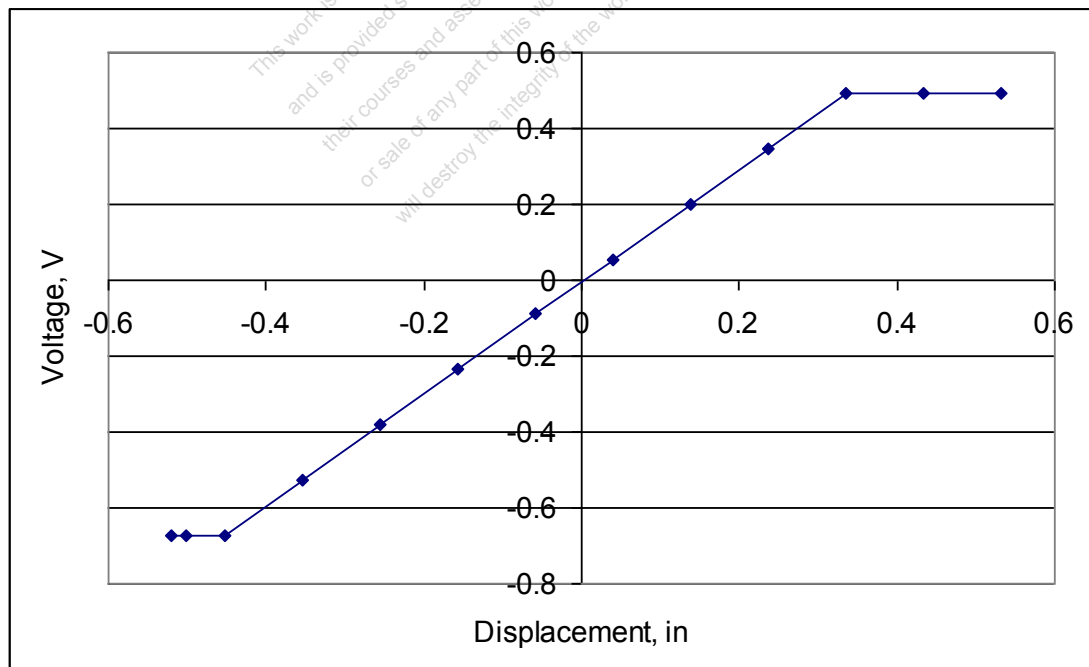

From the figure:

Linear range =  $\pm 0.3$  in.

Calibration factor = 1.47 Volts/in.

## CHAPTER 2. NATURE OF MATERIALS

- 2.1. See Section 2.2.1.
- 2.2. See Section 2.1.
- 2.3. See Section 2.1.1.
- 2.4. See Section 2.1.1.
- 2.5. See Section 2.1.2.
- 2.6. See Section 2.2.1.
- 2.7. See Section 2.1.2.
- 2.8. See Section 2.2.1.
- 2.9. See Section 2.2.1.
- 2.10. If the atomic masses and radii are the same, then the material that crystalizes into a lattice with a higher APF will have a larger density. The FCC structure has a higher APF than the BCC structure.

- 2.11. For the face-center cubic crystal structure, number of equivalent whole atoms in each unit cell = 4

By inspection the diagonal of the face of a FCC unit cell =  $4r$

Using Pythagorean theory:

$$(4r)^2 = a^2 + a^2$$

$$16r^2 = 2a^2$$

$$8r^2 = a^2$$

$$a = 2\sqrt{2}r$$

- 2.12. a. Number of equivalent whole atoms in each unit cell in the BCC lattice structure = 2

b. Volume of the sphere =  $(4/3) \pi r^3$

Volume of atoms in the unit cell =  $2 \times (4/3) \pi r^3 = (8/3) \pi r^3$

By inspection, the diagonal of the cube of a BCC unit cell

$$= 4r = \sqrt{a^2 + a^2 + a^2} = a\sqrt{3}$$

$$a = \text{Length of each side of the unit cell} = \frac{4r}{\sqrt{3}}$$